

# Tack Coat Effect on Field Performance



February 3rd, 2015  
NCAUPG/ICT Joint Meeting



**Road Science™**

Division of ArrMaz Custom Chemicals

# Bonded Pavement Experimentation

- What happens if significantly higher application rates are used?
- What forms of distress will appear or possibly be delayed?
- What effect does significantly different types of tack have on performance?
- Surface type effect on application rates (PCC, AC, milled)?



2008



2012



**Road Science™**

Division of ArrMaz Custom Chemicals

# What options are available to place tack uniformly without disturbing during construction?

- Modify the process to keep all construction equipment and trucks off the tack during construction
- Spray paver



# What is a Spray Paver?



Spray Paver = Paver + Distributor in one machine




**Road Science™**


Division of ArrMaz Custom Chemicals

# Spray Pavers

- Due to the distributor plus paver in one,
  - Different types of emulsion can be used
  - Dilution of emulsion is not required
  - Application rates are not limited by construction

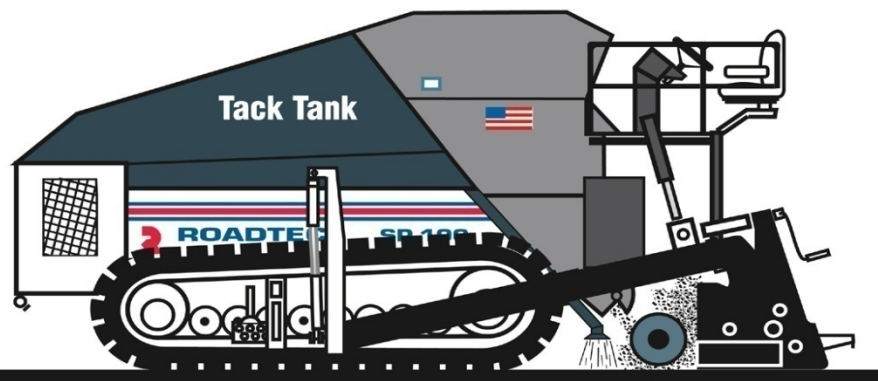

**ROADTEC STEALTH PAVER WITH TACK TANK**

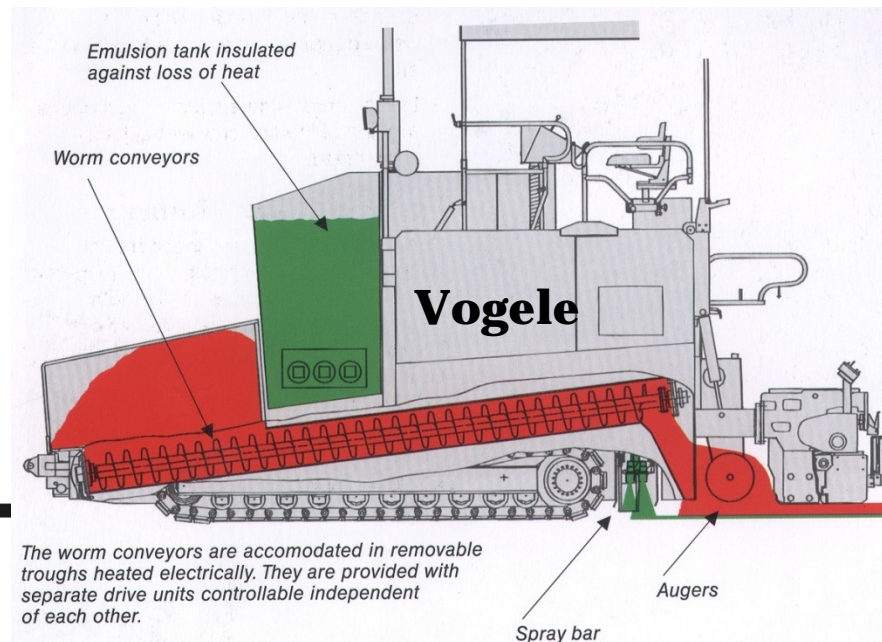

The worm conveyors are accommodated in removable troughs heated electrically. They are provided with separate drive units controllable independent of each other.

Spray bar

Augers

# Field Performance Data



# Route T, Franklin County, MO

- Constructed: October 2008
- Contractor: N.B. West
- Project length: 3.5 miles (test sections)
- Surface: Composite, HMA over PCC
- Mix: 1 ¾" Bonded BP-1 HMA w/ PG64-22
- Tack:
  - Test sections at 0.1, 0.15, and 0.2 gal/yd<sup>2</sup> PMAE at 65% AC
  - Test sections at 0.1 gal/yd<sup>2</sup> thru distributor and 0.1 and 0.15 gal/yd<sup>2</sup> CSS-1h thru SP-200
- Equipment: RoadTec SP-200 spray paver



June 2009




**Road Science**<sup>™</sup>

Division of ArrMaz Custom Chemicals


# MoDOT Route T Project – Oct 2008

## 1 3/4" BP-1 overlay over composite pavement

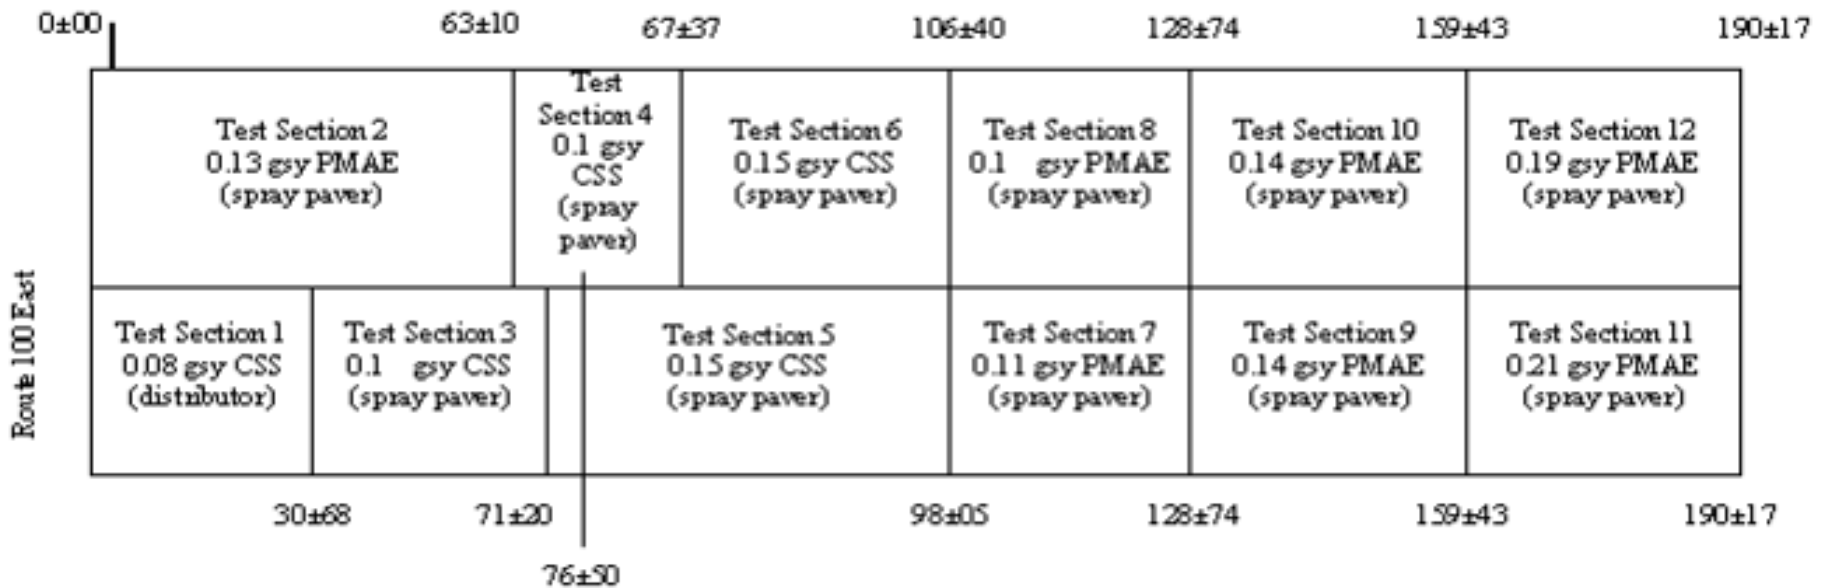




# MoDOT Route T 2008 @ 68 months 1 3/4" BP-1 over HMA/PCC Composite Transverse Crack Length/1000' vs Time West Bound Lane

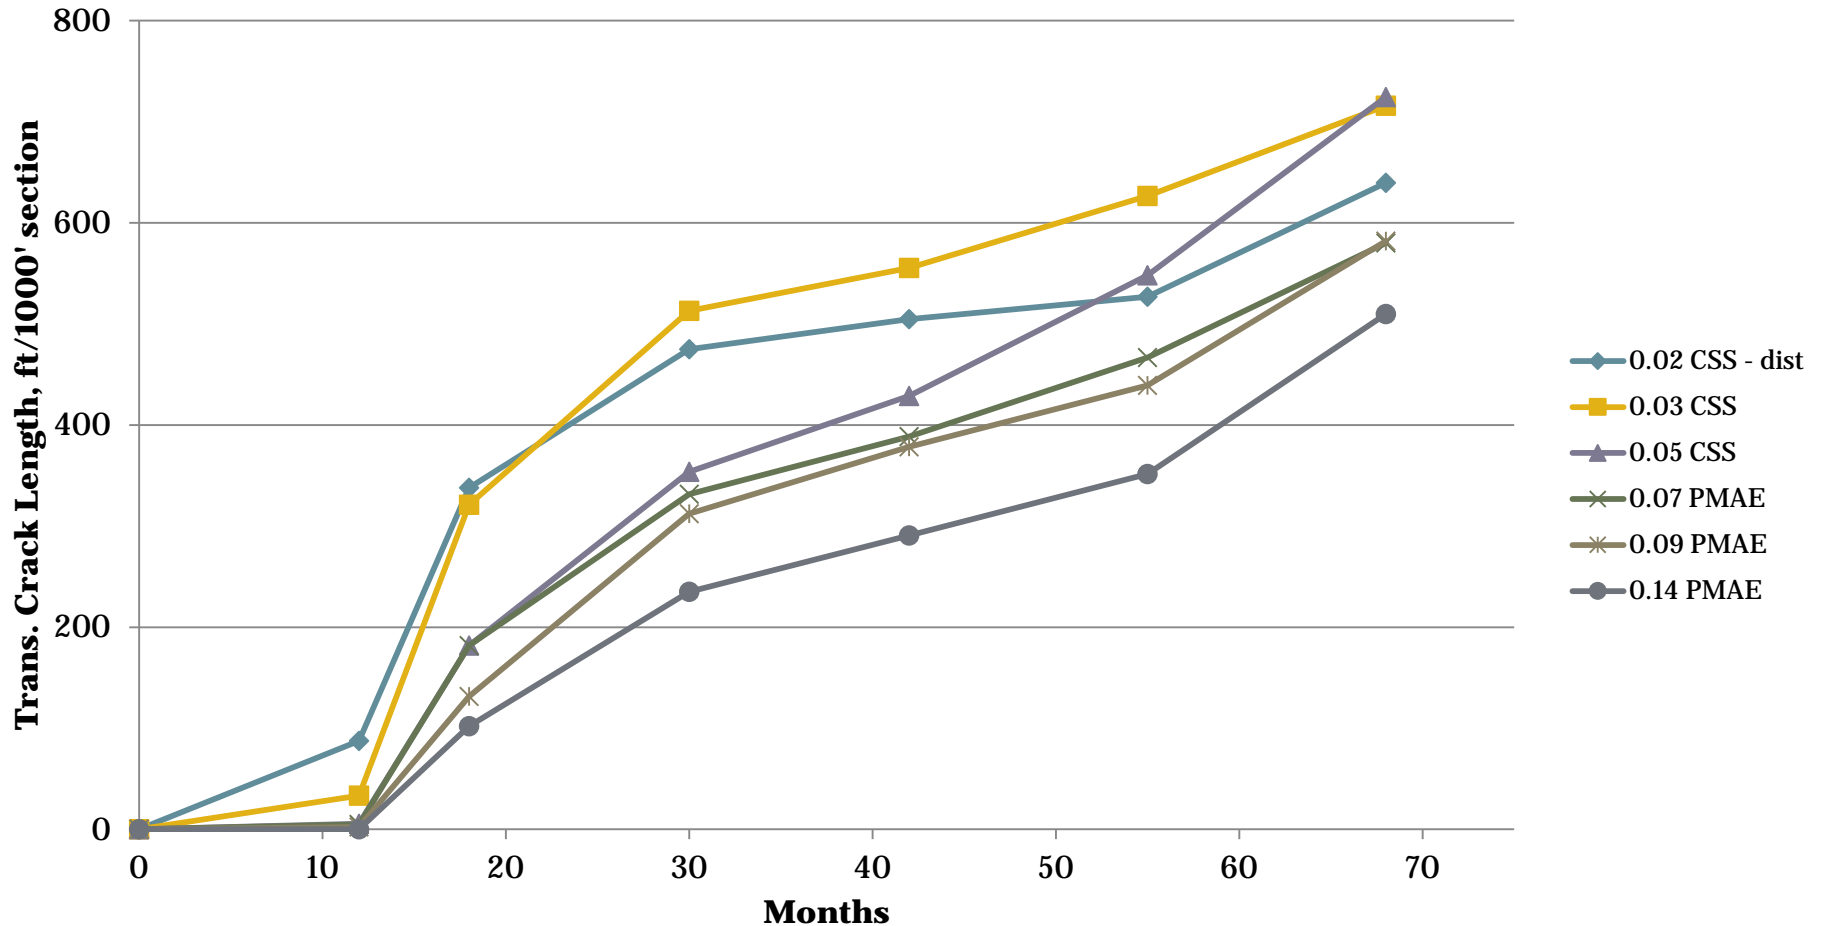

# MoDOT Route T 2008 @ 68 months 1 ¾" BP-1 over HMA/PCC Composite Longitudinal Crack Length/1000' vs Time West Bound Lane

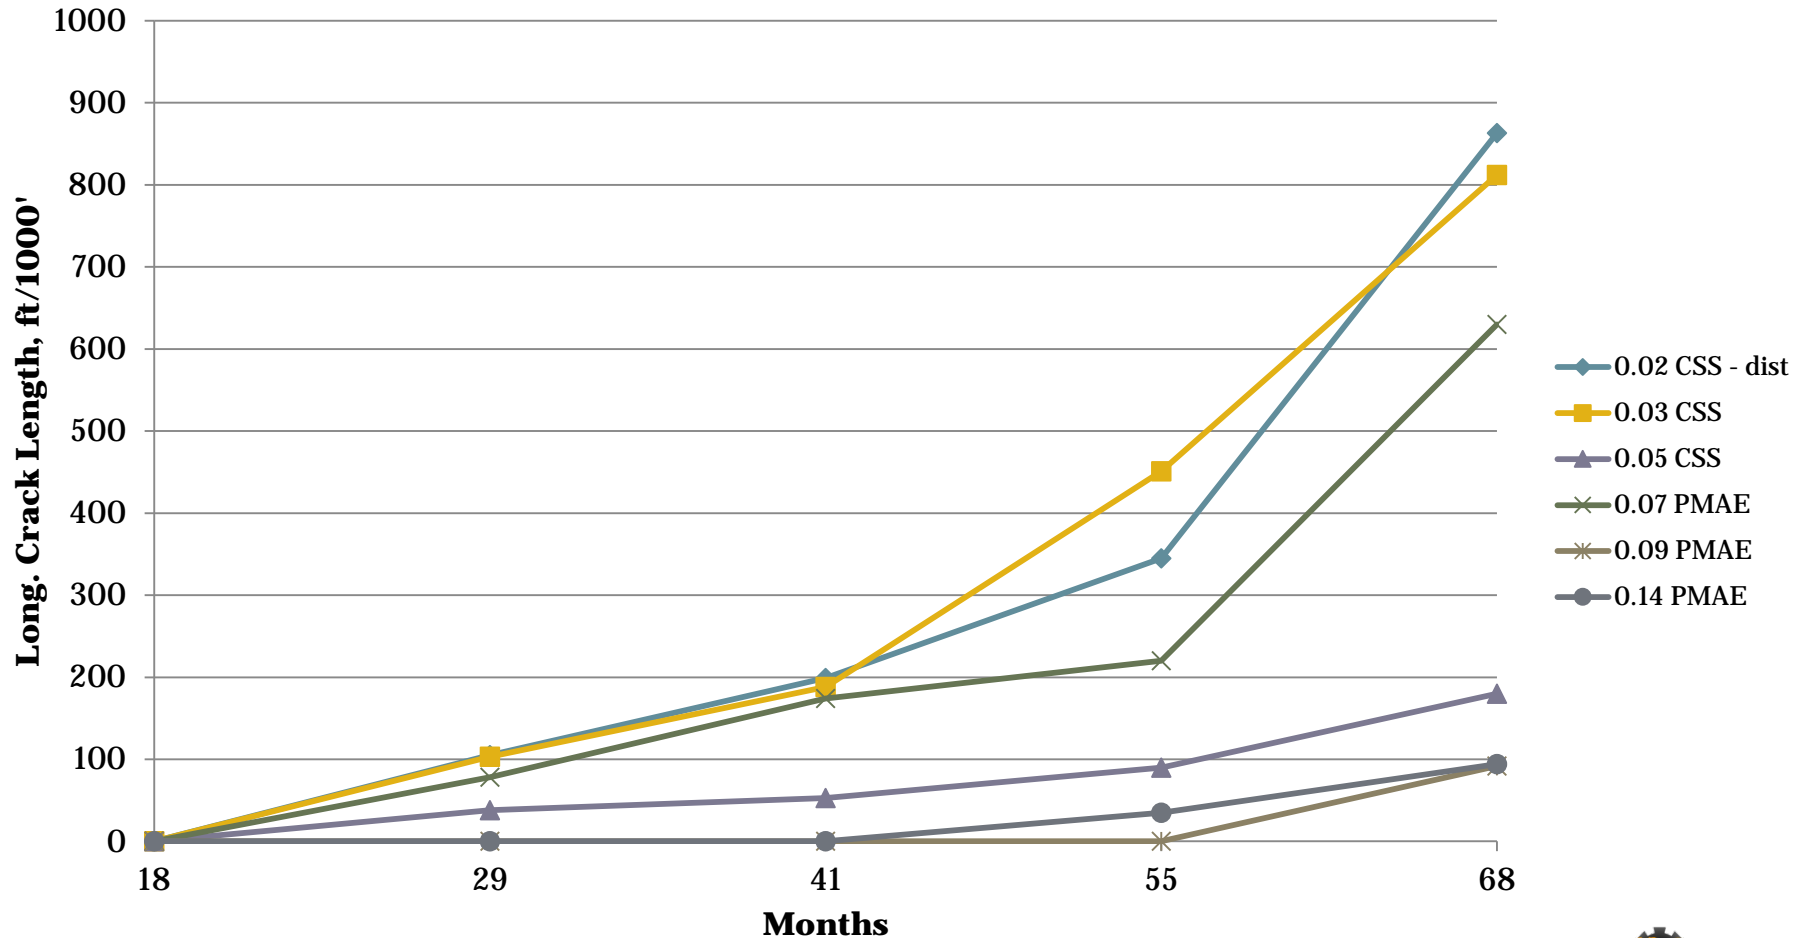

# Route T Franklin Co Test Sections 11/12

## Pre-paving and 4 years later



2008



2012

0.21 gal/yd<sup>2</sup> (0.14 res) PMAE Tack



**Road Science™**

Division of ArrMaz Custom Chemicals

# Route T Franklin Co Test Sections 11/12 Pre-paving and 6 years later



2008



2014

0.21 gal/yd<sup>2</sup> (0.14 res) PMAE Tack



**Road Science™**

Division of ArrMaz Custom Chemicals

# KDOT US 36 Washington Co. Project – Sept 2009

## 1 1/2" SR-12.5A over a Milled Surface




<b>Test Section 11</b> 40% RAP 0.35 gal/yd <sup>2</sup> EBL	<b>Test Section 10</b> 40% RAP 0.25 gal/yd <sup>2</sup> EBL	<b>Test Section 9</b> 25% RAP 0.12 gal/yd <sup>2</sup> EBL	<b>Test Section 7</b> 25% RAP 0.20 gal/yd <sup>2</sup> EBL	<b>Test Section 5</b> 25% RAP 0.16 gal/yd <sup>2</sup> EBL	<b>Test Section 3</b> 25% RAP 0.08 gal/yd <sup>2</sup> EBL	<b>Test Section 1</b> 25% RAP No Tack
		<b>Test Section 8</b> 25% RAP 0.12 gal/yd <sup>2</sup> CSS-1h	<b>Test Section 6</b> 25% RAP 0.20 gal/yd <sup>2</sup> CSS-1h	<b>Test Section 4</b> 25% RAP 0.16 gal/yd <sup>2</sup> CSS-1h	<b>Test Section 2</b> 25% RAP 0.08 gal/yd <sup>2</sup> CSS-1h	



# KDOT US 36 Washington Co 2009 at 43 months

## 1/2 Mill, 1 1/2" SR12.5A, PG58-28


### Transverse Cracking/1000' section vs Time

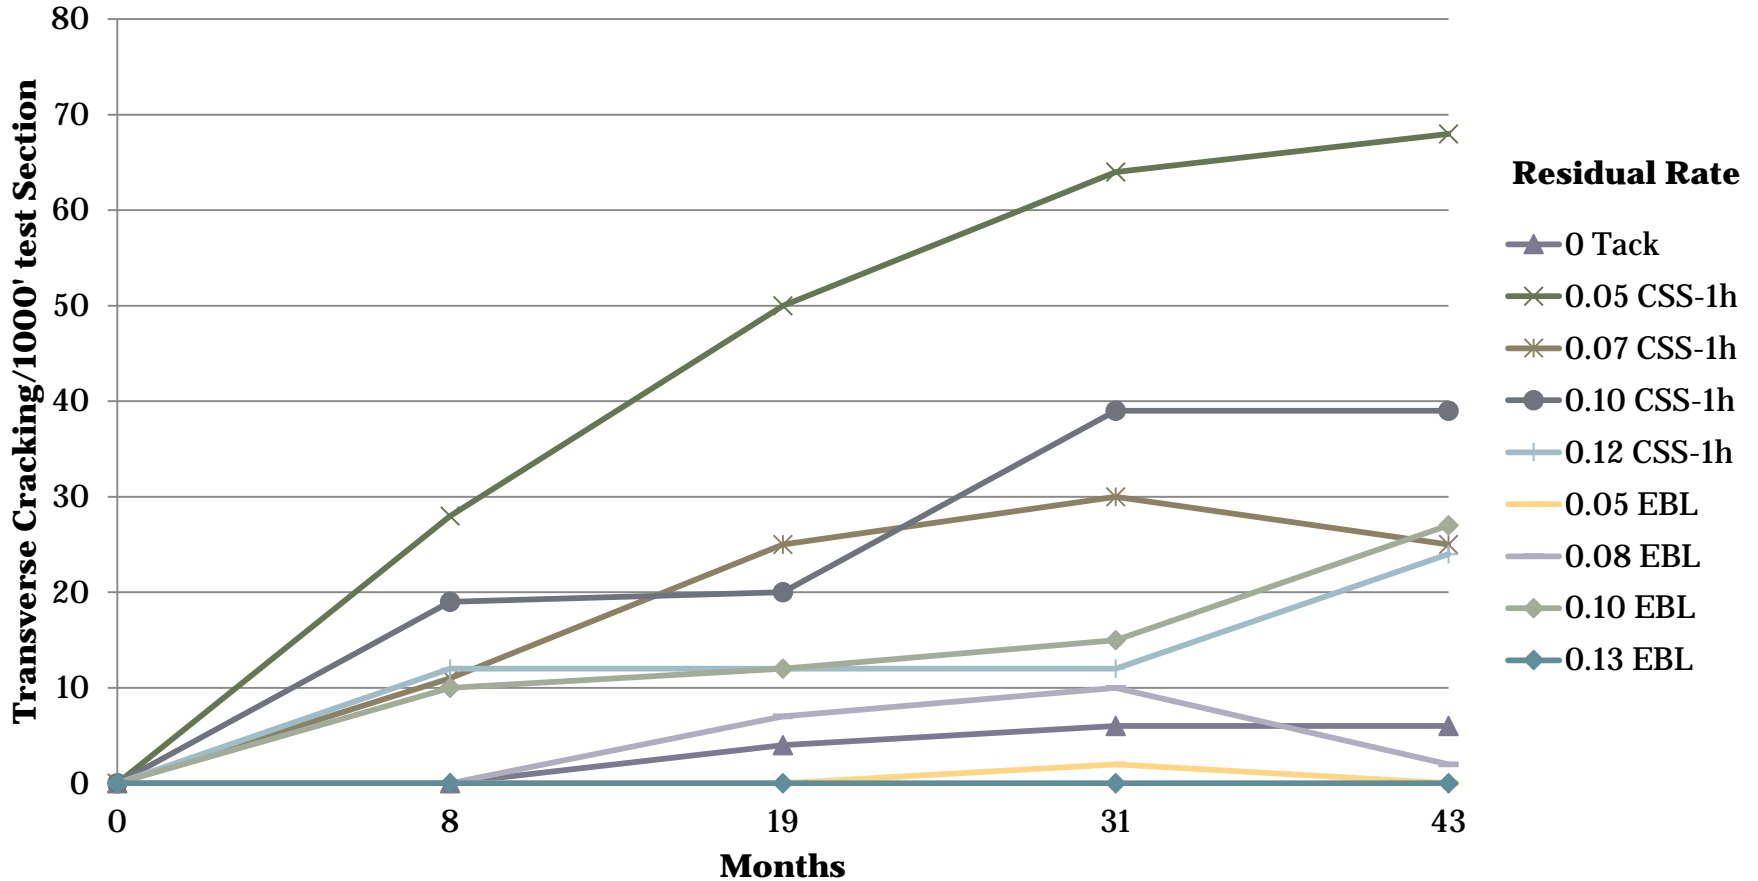

# KDOT US 36 Washington Co. at 43 months

## 1/2" Mill, 1 1/2" SR12.5A, PG58-28


### Longitudinal Cracking/1000' section vs Time

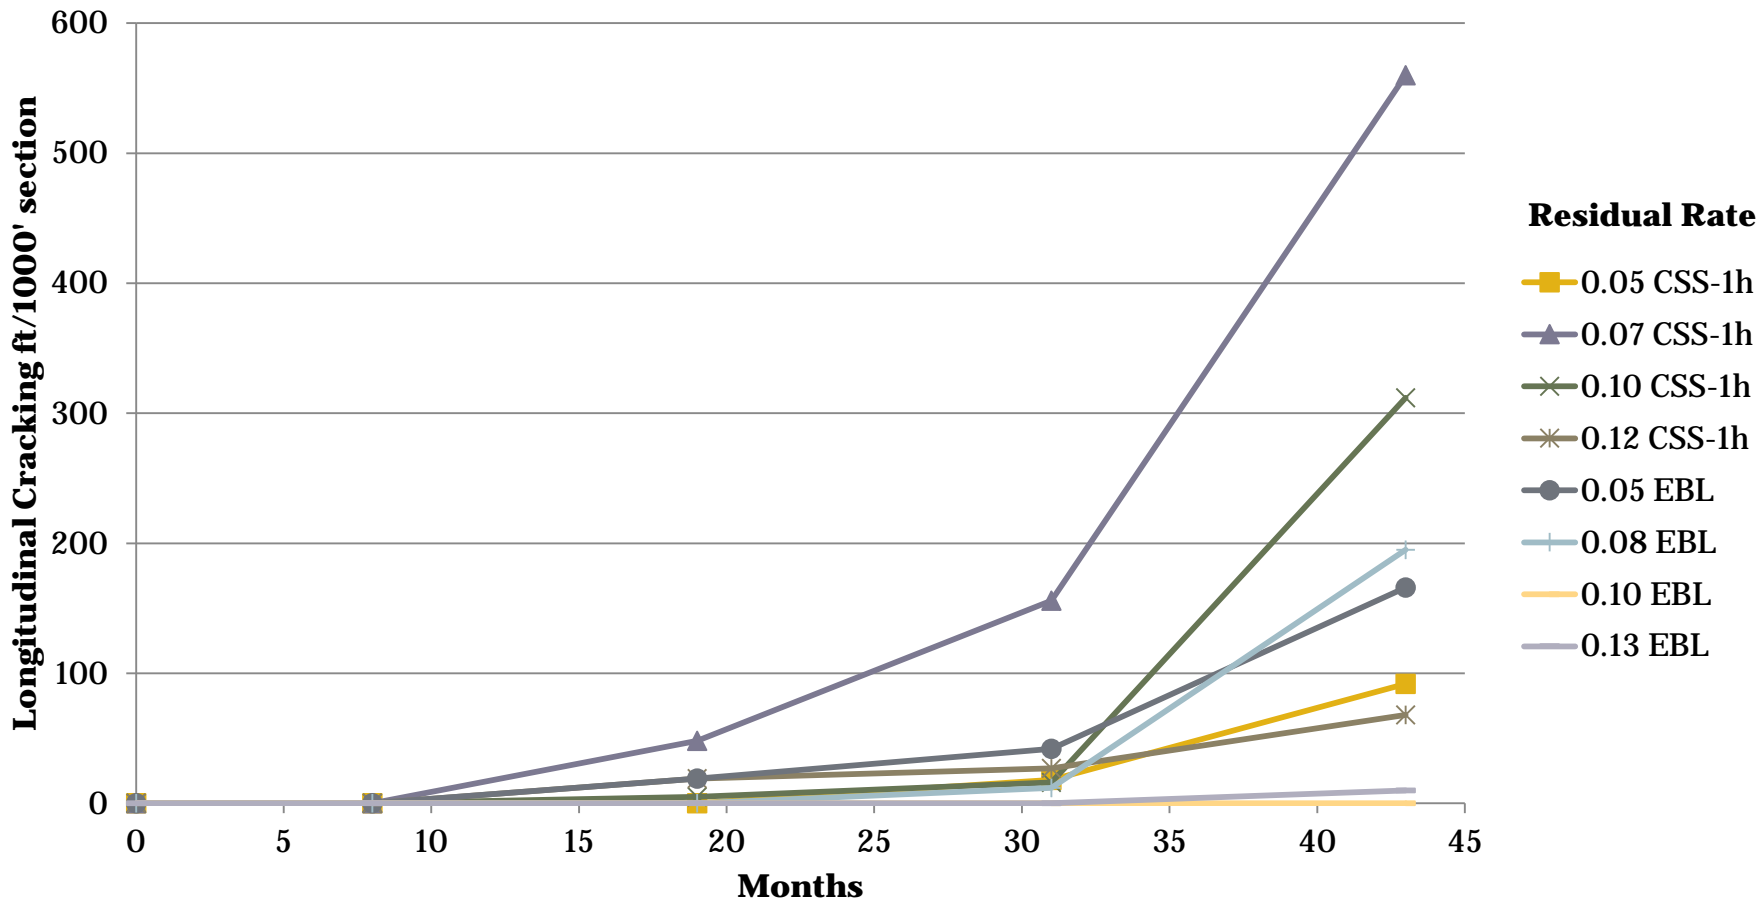

# KDOT US 36 Washington Co. at 43 months

## 1/2" Mill, 1 1/2" SR12.5A, PG58-28

### Longitudinal Cracking/1000' section vs Time

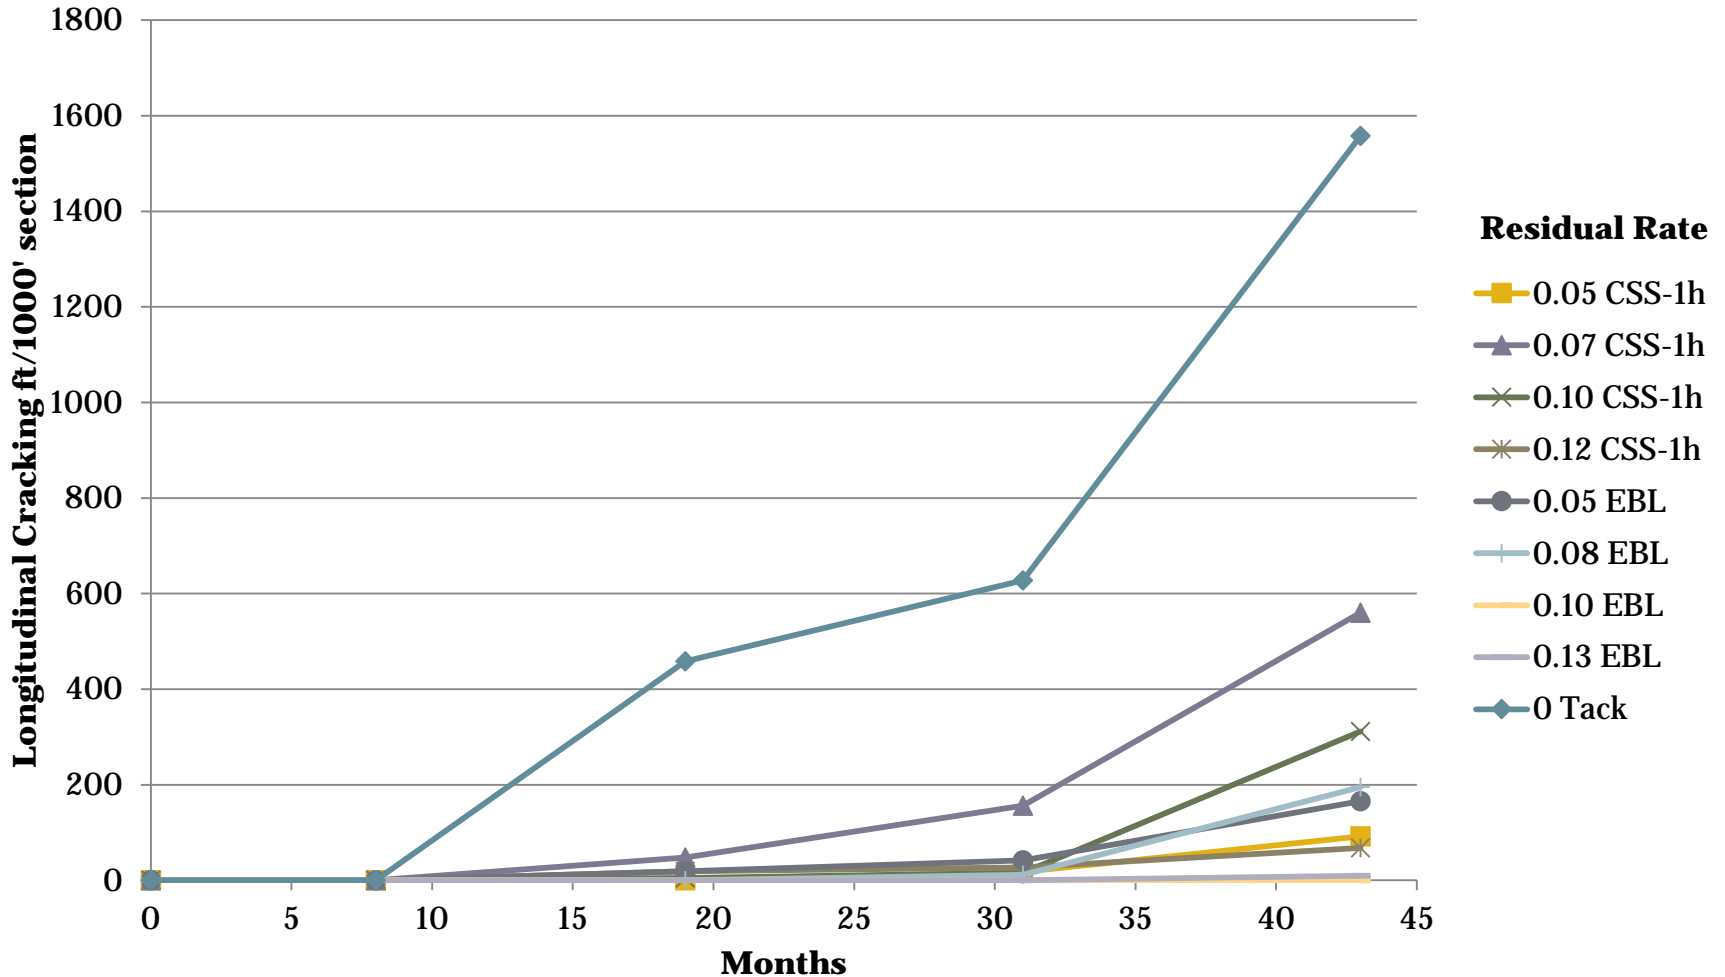




# No Tack over a Milled Asphalt Surface US 36 Washington Co. KS 2009




# KDOT US 36 Marshall Co. (Const. 2010)

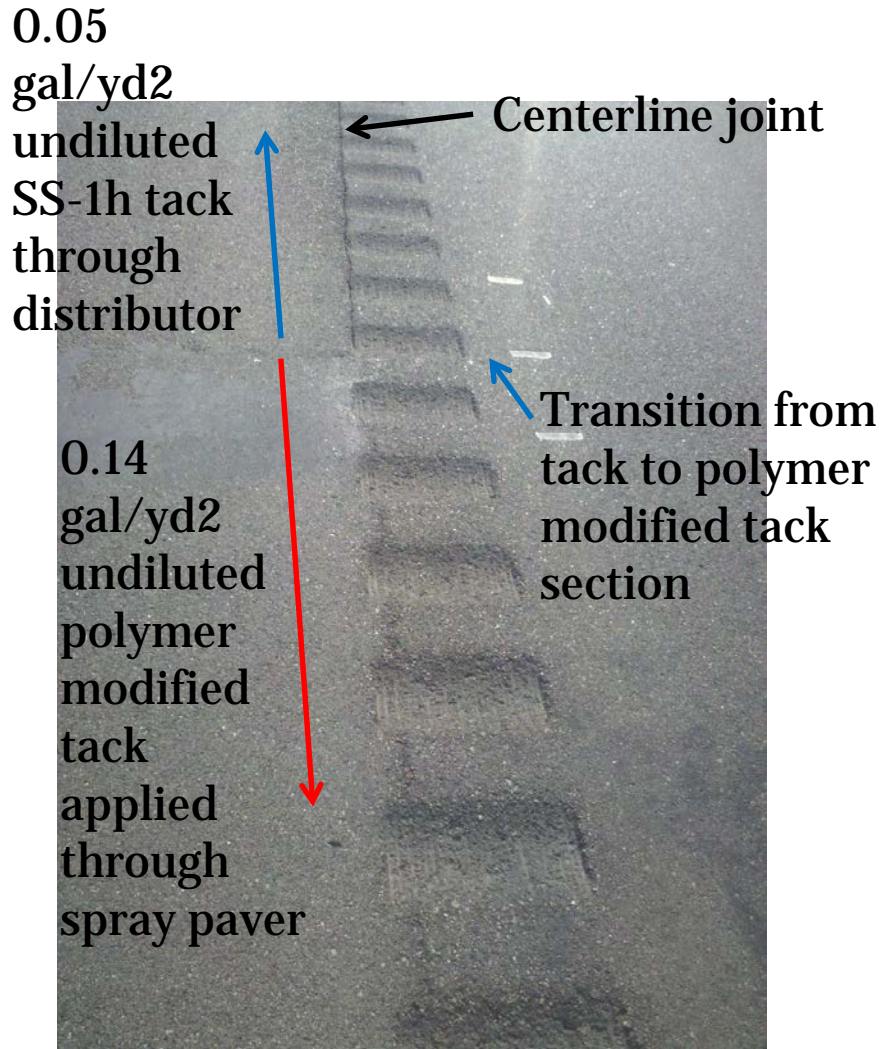


- 1" mill, 1" SR9.5A
- PG70-28 binder
- 5 test sections
  - 4 spray paver shot rates
    - 0.11 gal/yd<sup>2</sup> EBL
    - 0.18 gal/yd<sup>2</sup> EBL
    - 0.26 gal/yd<sup>2</sup> EBL
    - 0.36 gal/yd<sup>2</sup> EBL
  - 1 Distributor applied shot rate
    - 0.05 gal/yd<sup>2</sup> SS-1h



# KDOT US 36 Marshall Co. 2010 Transverse Cracking at 43 months 1" Mill, 1" SR9.5A, PG70-28

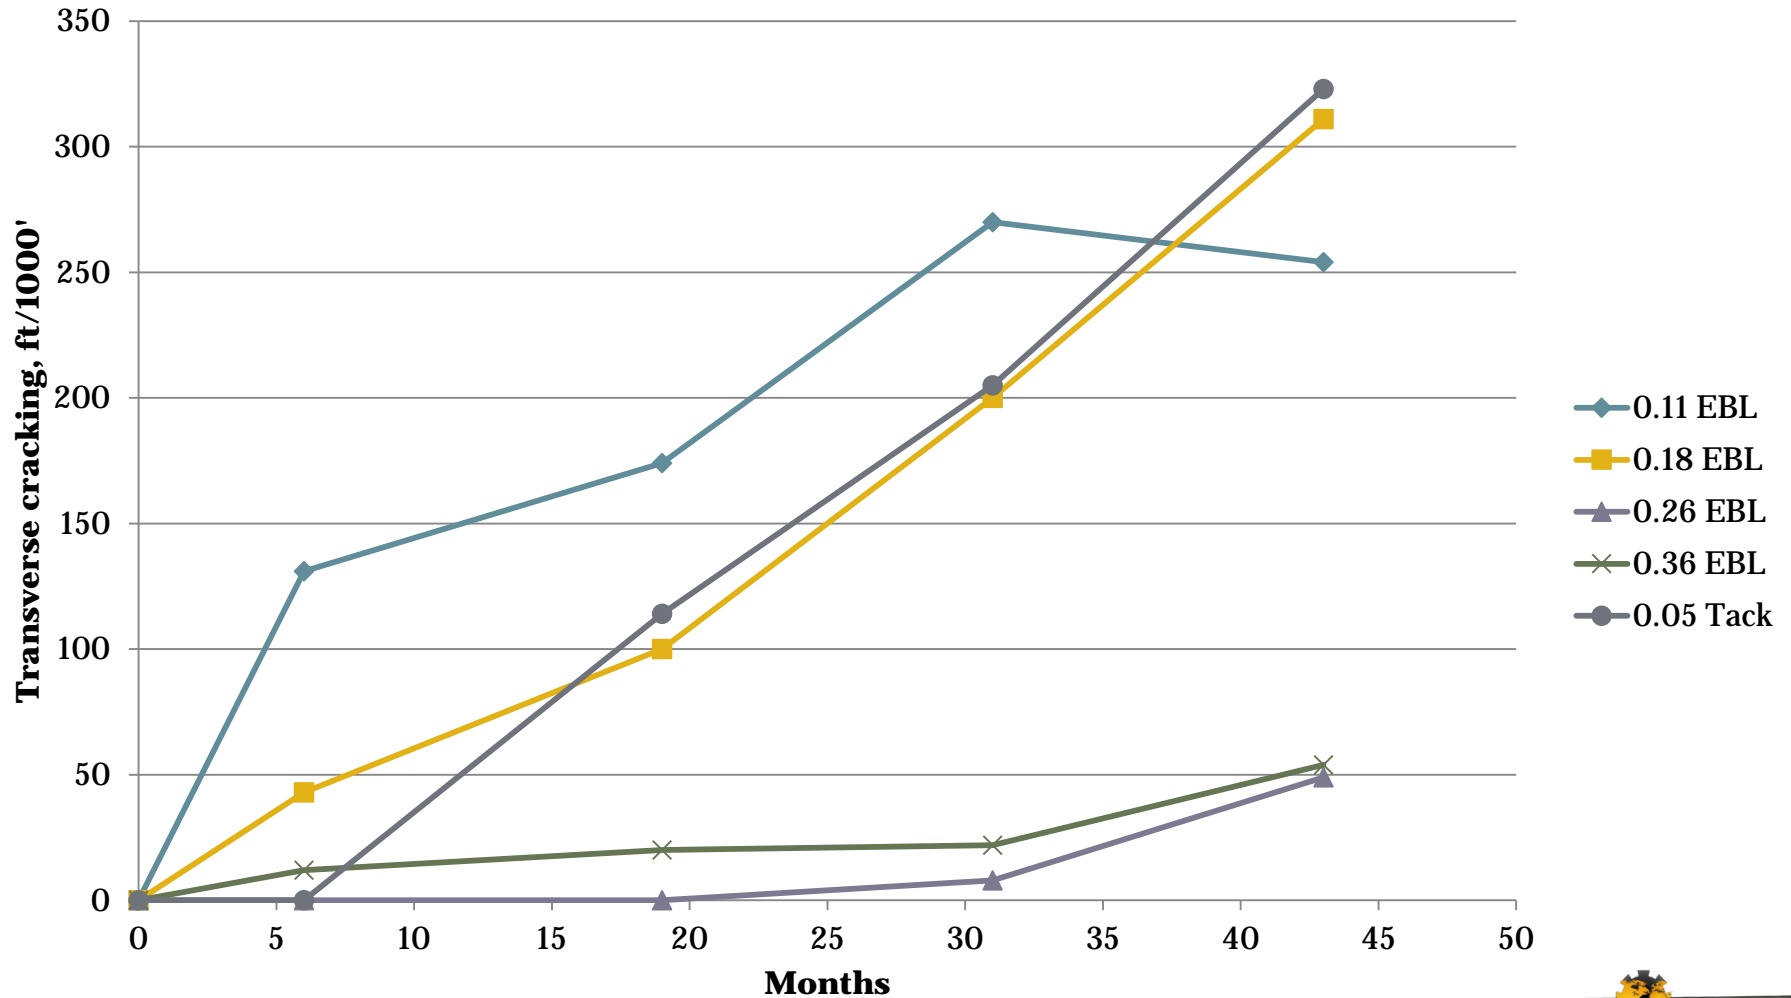

# KDOT US 36 Marshall Co. 2010 Longitudinal Cracking at 43 months 1" Mill, 1" SR9.5A, PG70-28

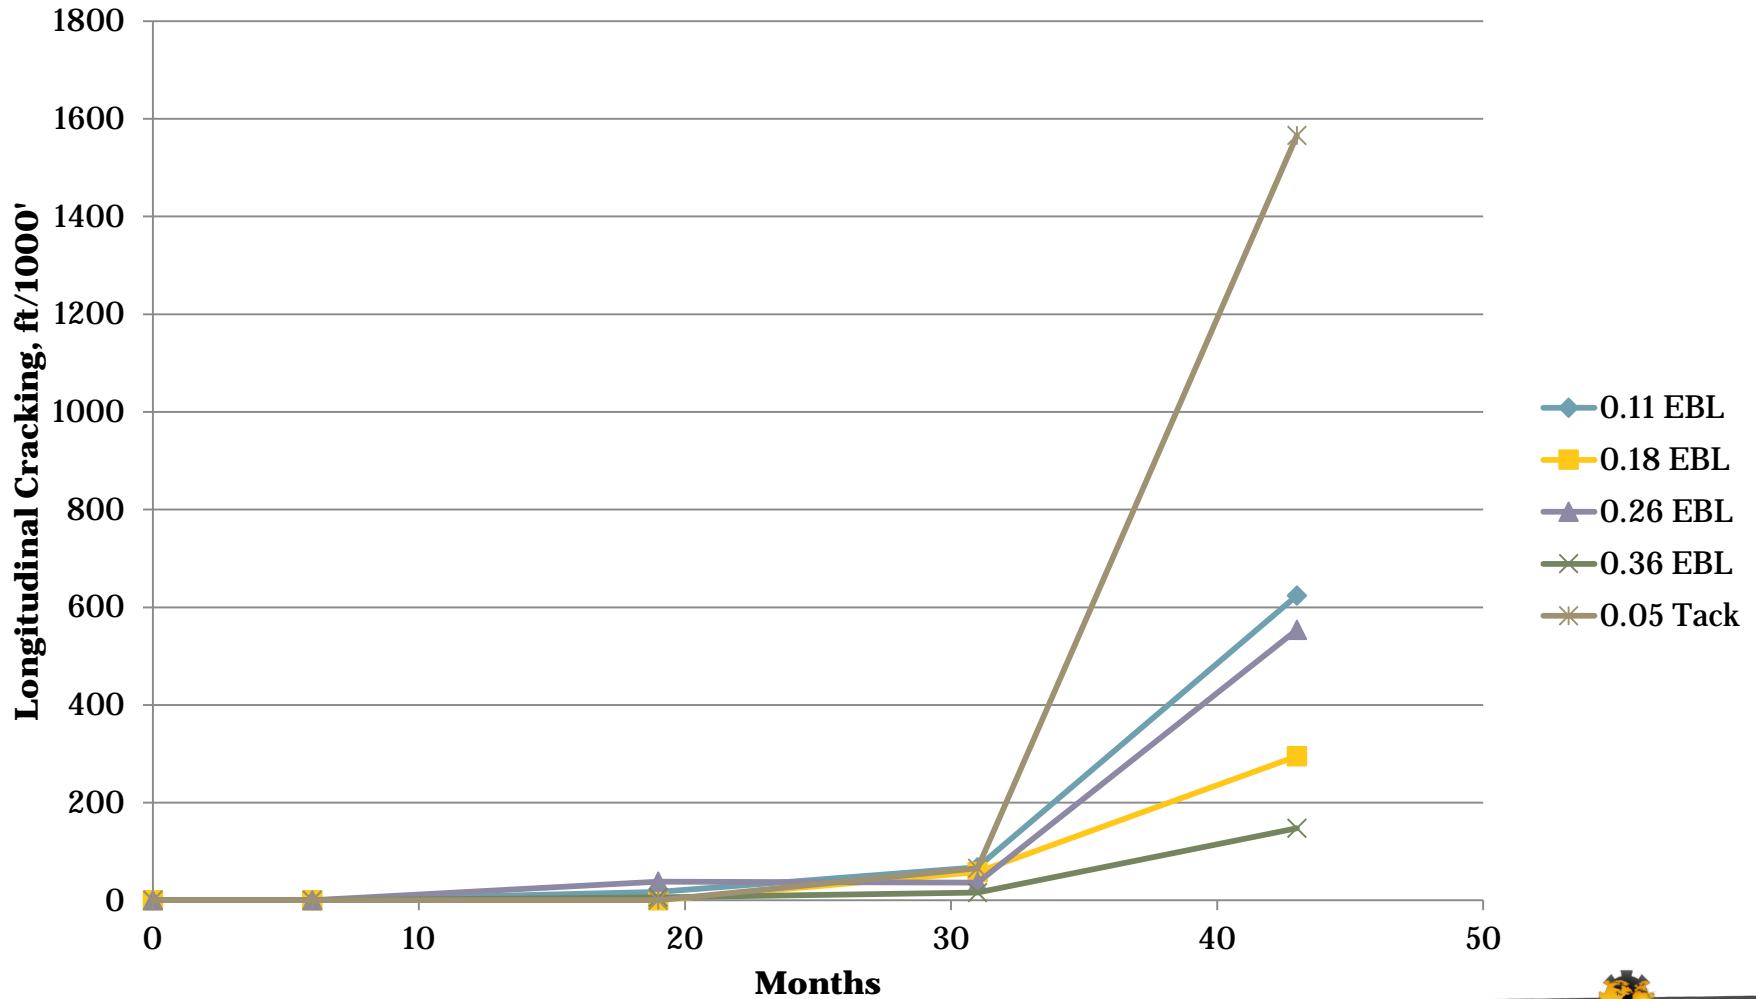


# KDOT US 36 Nemaha County 2010


- 4" CIR with emulsion
- 1 ½" SR12.5A
- PG70-22 binder
- 4 Test sections
  - 3 spray paver shot rates
    - 0.11 gal/yd<sup>2</sup> EBL
    - 0.22 gal/yd<sup>2</sup> EBL
    - 0.34 gal/yd<sup>2</sup> EBL
  - 1 distributor applied control section
    - 0.05 gal/yd<sup>2</sup> CSS-1h



# KDOT US 36 Nemaha Co. 2010 Transverse Cracking at 41 months 4" CIR w/ 1 1/2" SR12.5A, PG70-22

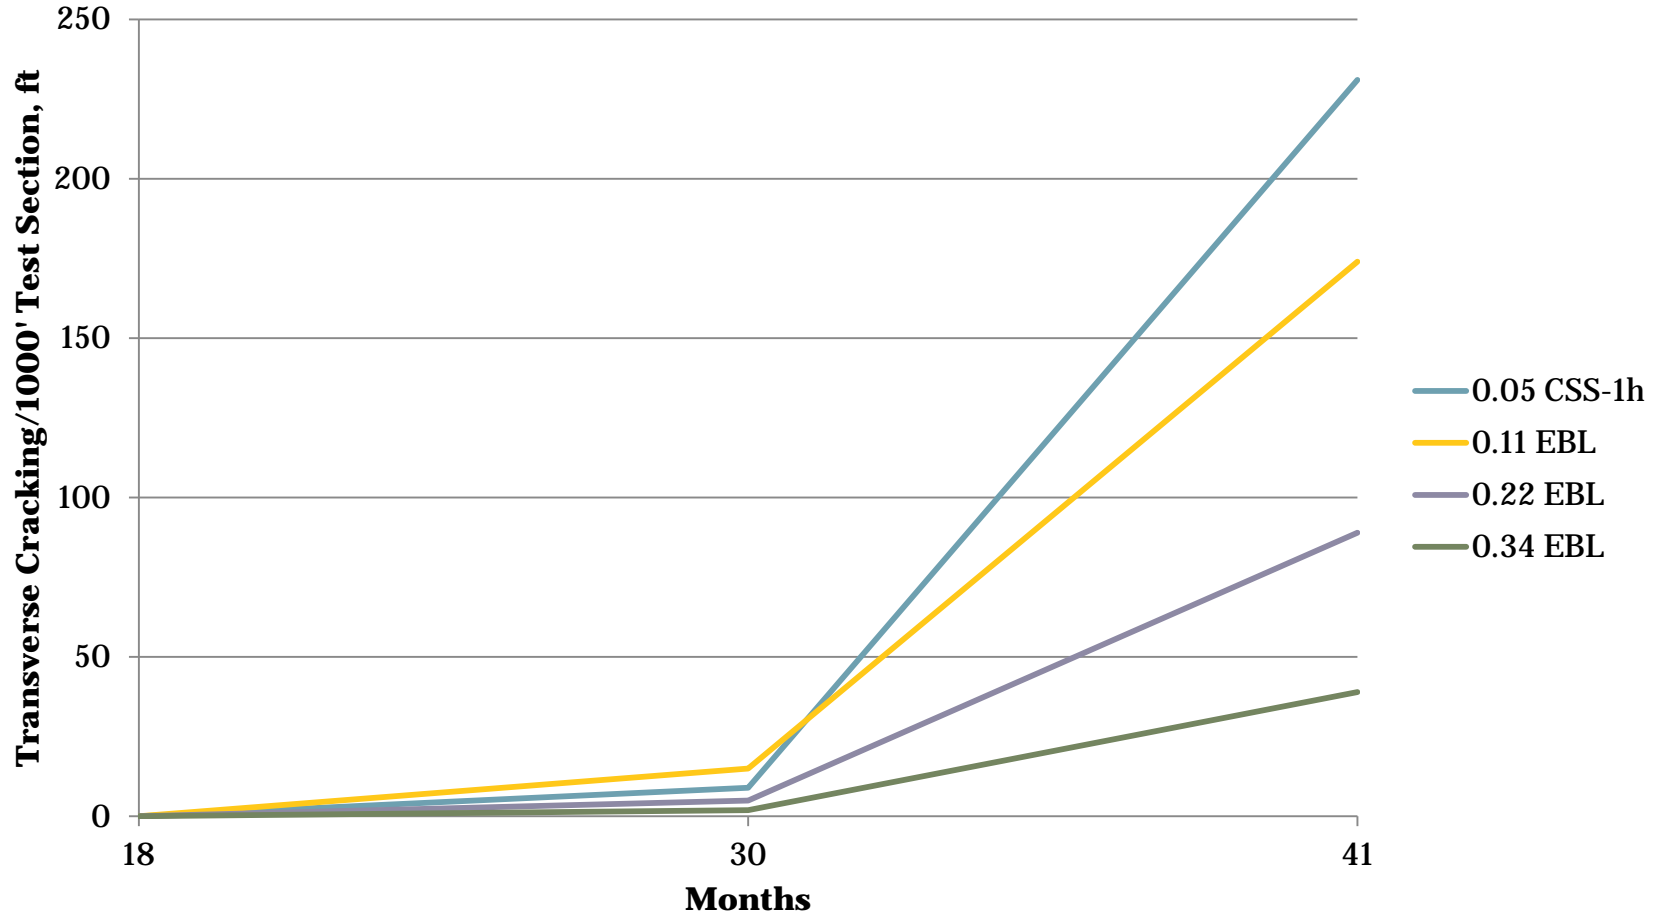


# KDOT US 36 Nemaha Co. 2010 Longitudinal Cracking at 41 months 4" CIR w/ 1 1/2" SR12.5A, PG70-22

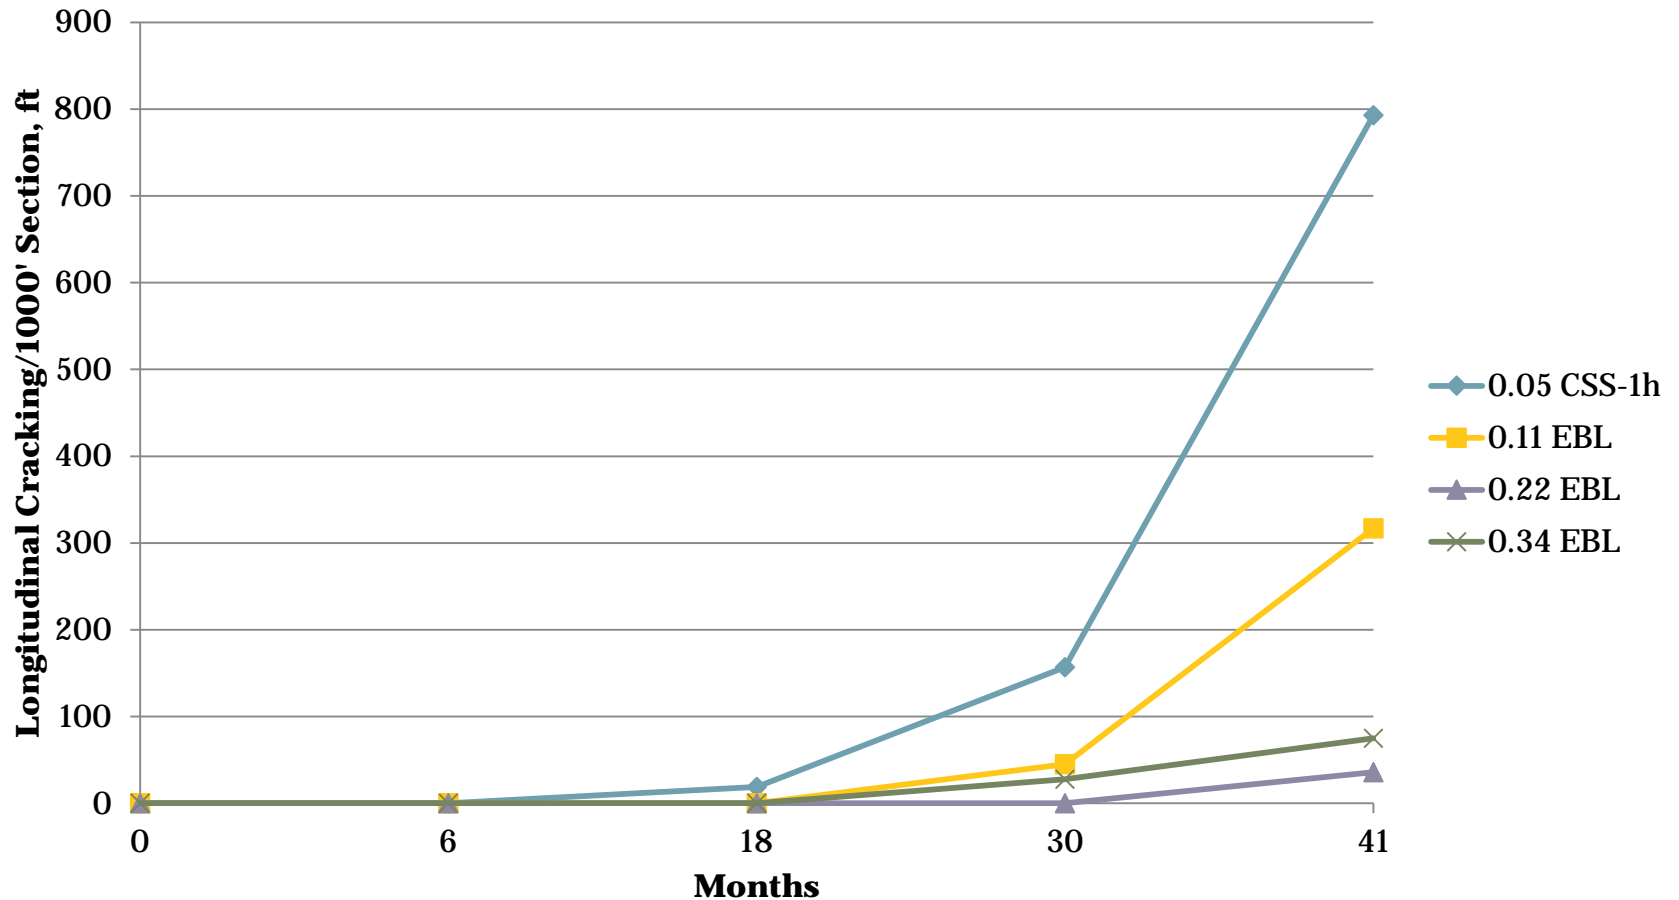

# Saturation at Interface Creates Voidless Height in HMA

- Higher tack rate creates an asphalt rich interlayer at the interface with the existing pavement

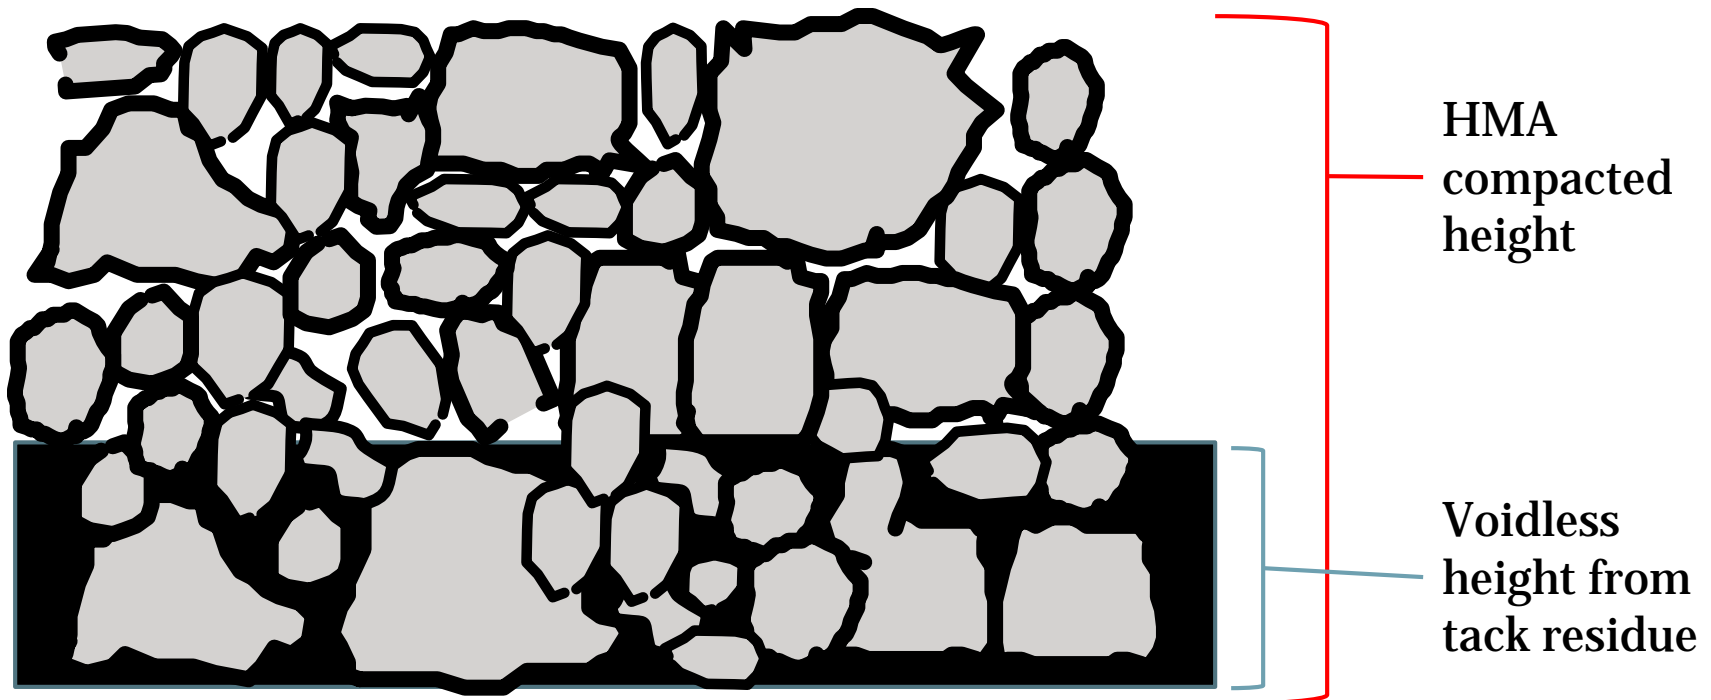


Bonded to existing pavement surface






## MoDOT Route T @ 41 months Transverse Cracks vs Voidless Height

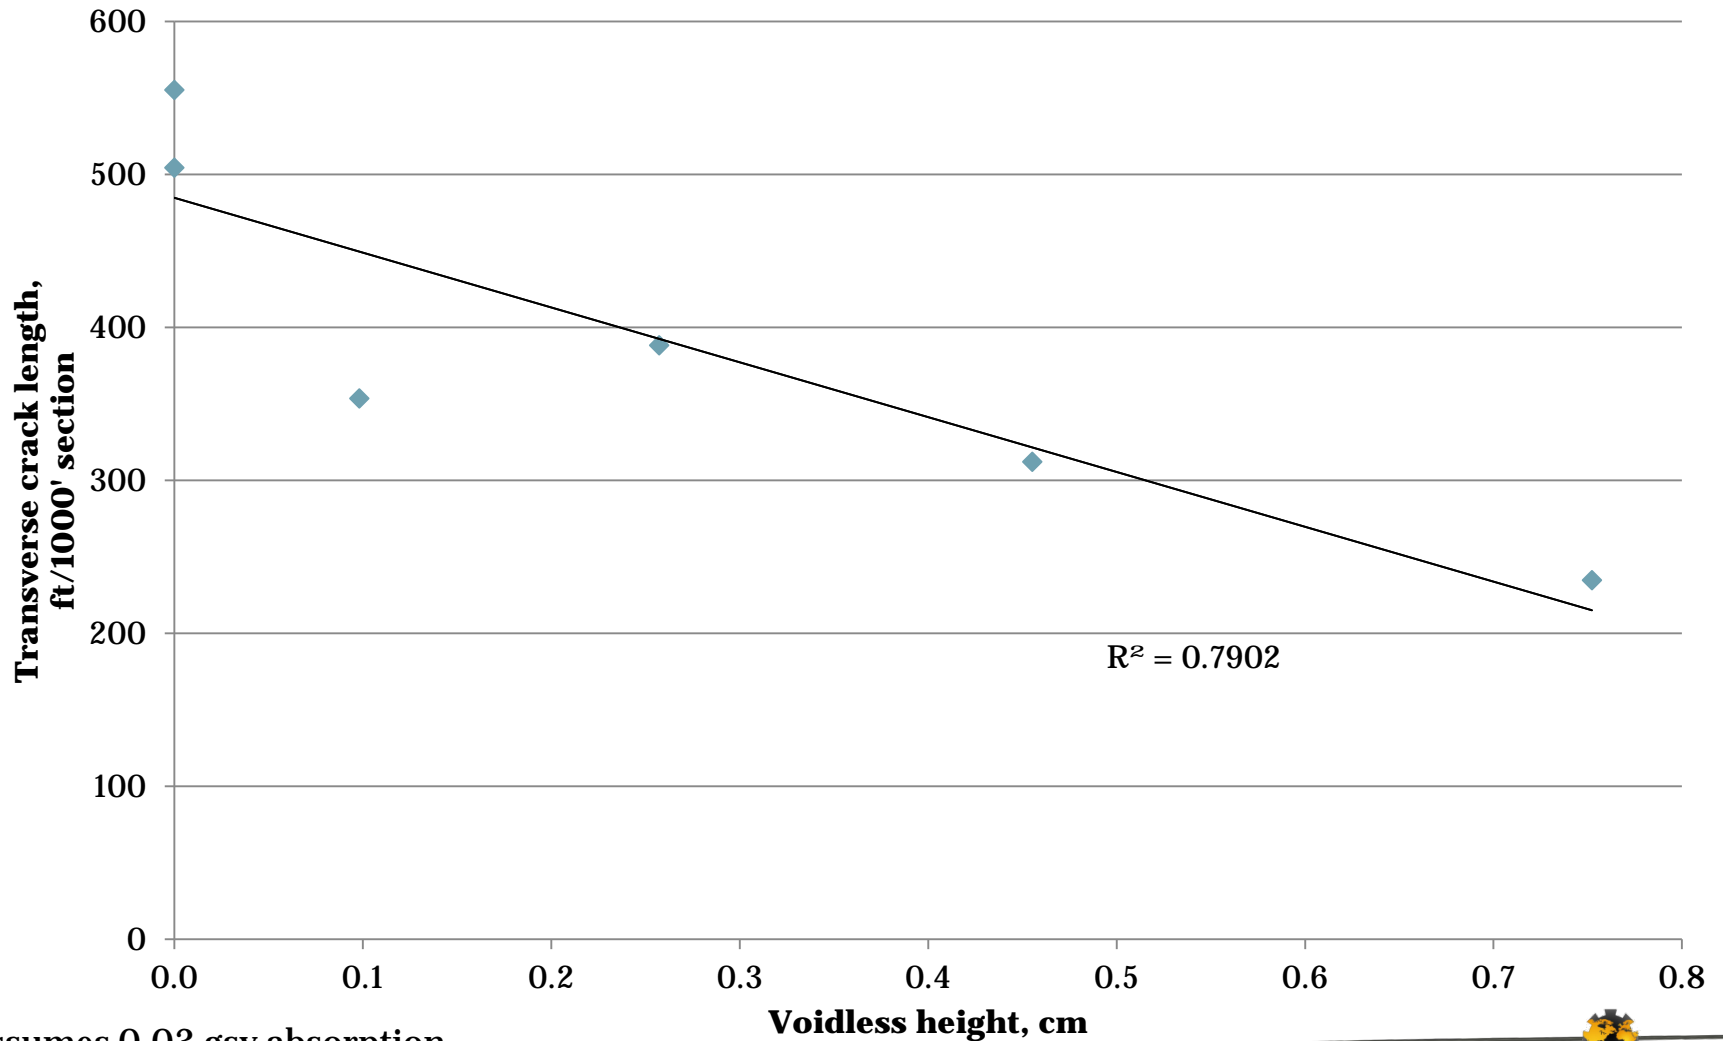

\*Assumes 0.03 gsy absorption



# US 36 Nemaha County, KS @ 41 Months Transverse Cracks vs Voidless Height

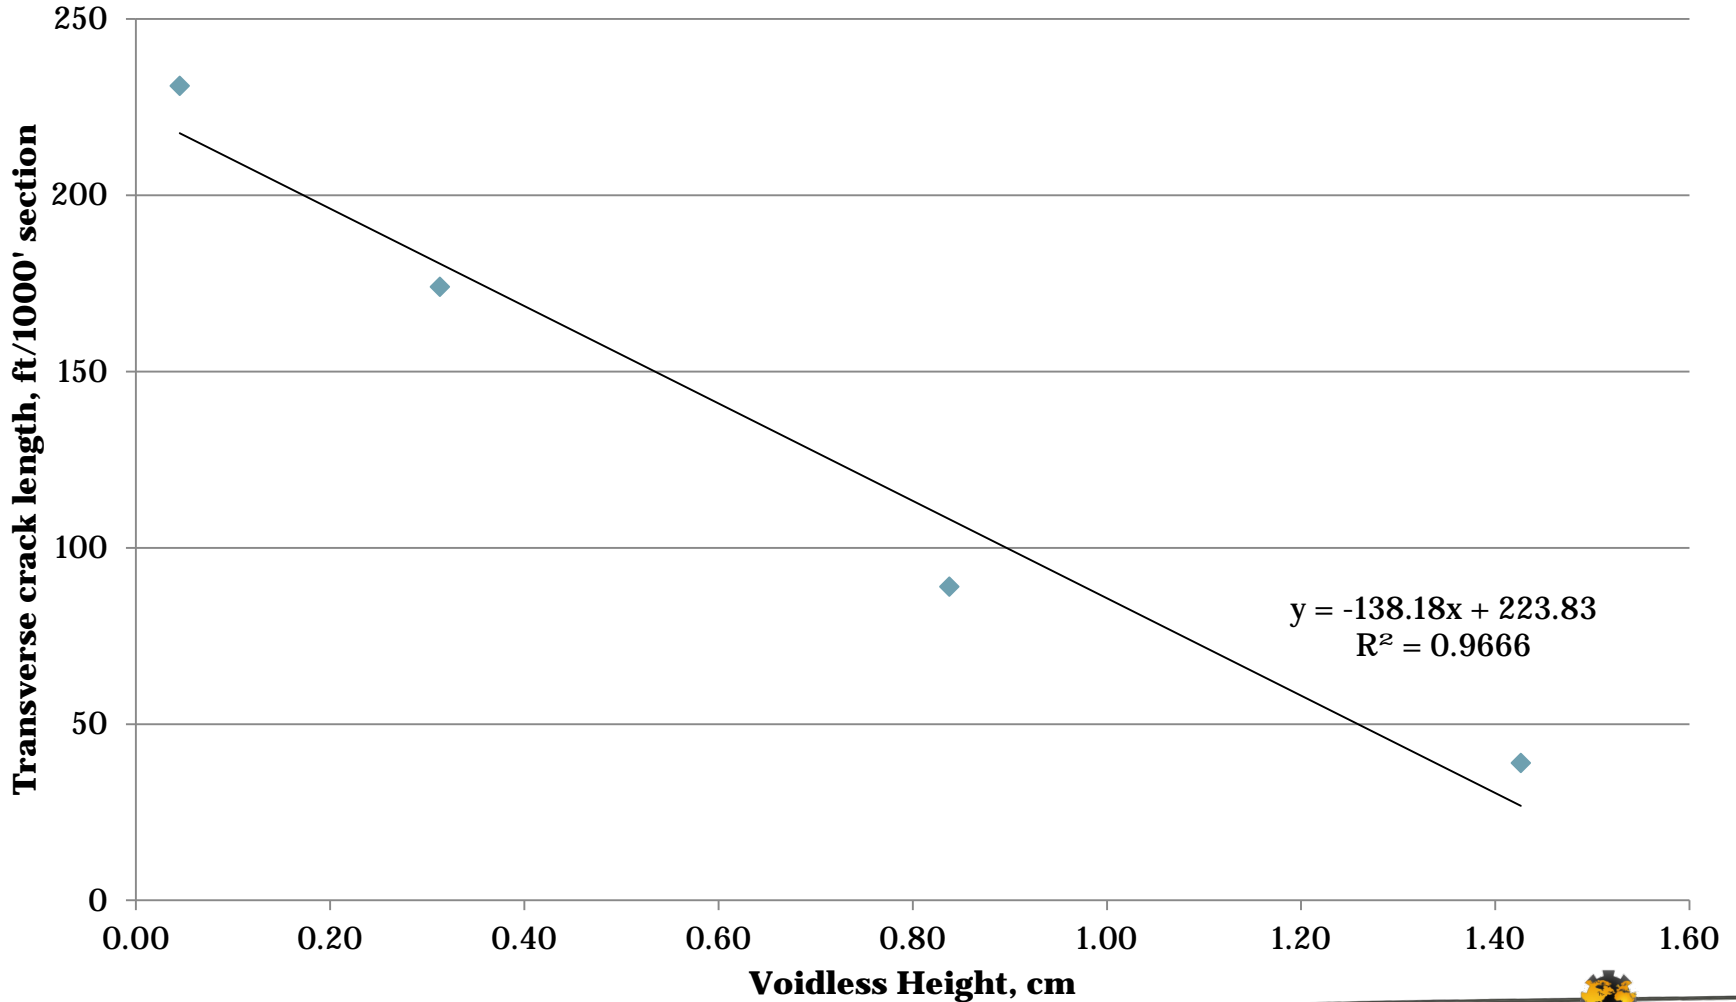

# Observations from Field Performance

- Based on field project data,
  - Correlation of bond energy to longitudinal cracking resistance exists
  - Correlation of voidless height to transverse cracking exists
  - General trends favor higher application rates (than standard tack rates) and polymer modified tack
    - Improved mix performance; more resistance to transverse and longitudinal cracking
  - Field data from more projects are being gathered



# Questions?

